

REVIEW

FROM MICROMECHANICS TO STRUCTURAL ENGINEERING —THE DESIGN OF CEMENTITIOUS COMPOSITES FOR CIVIL ENGINEERING APPLICATIONS

Victor C. LI

Advanced Civil Engineering Materials Research Laboratory
(ACE-MRL)

Department of Civil and Environmental Engineering,
University of Michigan, Ann Arbor, MI 48109-2125

Key Words : *pseudo strain-hardening, cement based composites, design, micromechanics, structures, properties.*

ABSTRACT

This paper reviews the development of pseudo strain-hardening cement based short fiber composites employing the Performance Driven Design Approach. The micromechanics theory behind the design concept is reviewed, and the unique mechanical properties of the resulting composite are summarized. The translation of material properties to structural properties is demonstrated with the structural response of the Ohno shear beam.

INTRODUCTION

The field of structural engineering and the field of micromechanics appear far and wide apart. Recent developments, however, point to a common ground—Materials. Advanced Civil Engineering materials are being developed with the help of micromechanics. And advanced materials are increasingly recognized as an enabling technology for the building and construction industries¹⁾. A new breed of engineers is needed to exploit the merits of this interdisciplinary field of materials design for structural applications.

This paper surveys the experience of such a research/education program at the University of Michigan. It reviews the framework of the interconnections between structural performance, materials properties, microstructures and materials processing, applied specifically to cementitious composites to be used in shear intensive load bearing structures. The concept of micromechanics deployed for materials development is emphasized, and the resulting advantages in structural performance improvements are highlighted.

PERFORMANCE DRIVEN DESIGN AND THE ACE-MRL

The Performance Driven Design Approach (PDDA)²⁾ is based fundamentally on the paradigm of materials development as proposed by the United States National Research Council³⁾. This paradigm emphasizes the interrelationships between performance-(material) structure-property-processing (Fig.1). Note the role of micromechanics as a quantitative link between material structure and mechanical properties.

Structural performance has usually been the domain of the structural engineer, who traditionally has been trained to build the best structures using given materials. For this reason, his/her connection to materials is mostly through materials property testing or property table look-up. The traditional material scientists are mostly concerned with the relationship between processing and formation of microstructures, and the traditional materials engineer can be said to be most interested in the resulting property of the material as influenced by processing. The interrelationship between microstructures and properties engages the applied mechanicians.

The paradigm in Fig.1 suggests that the materials scientists and engineers, the applied mechanicians and the structural engineers should all work together. Unfortunately this is usually not the case, especially with regard to materials used for the building and construction industries. In fact, building and construction materials, which may be characterized as high volume low cost materials, do not normally attract the attention of the materials scientist and engineers. As a result, the building and construction industries are, in general, well behind many other industries in the development


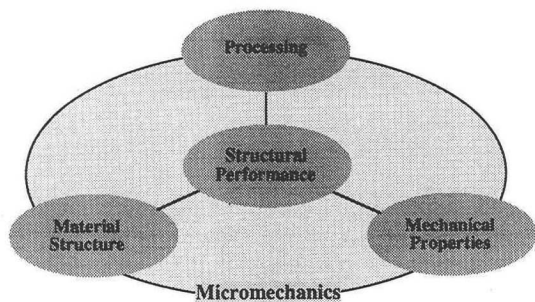


Fig.1 Paradigm of Materials Development.

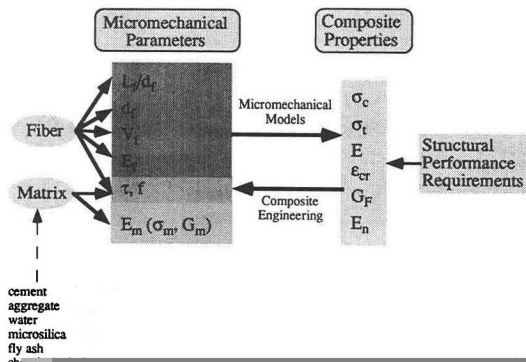

micromechanisms of deformation. For cementitious composites in which the matrix is brittle, extension of microcracks, and fiber/matrix interaction represent some of the most dominant deformation micromechanisms. Micromechanics creates the possibility of predicting the properties of a composite for a given material structure, and also provides guidance to composite microstructure optimization.

In a FRCC, the material microstructures can be characterized by measurable parameters related to the cementitious matrix (modulus, porosity, flaw density and size distribution, fracture property), the fiber (modulus, strength, bundle sizes, length, diameter, shape), and the interface (bond mechanisms and properties, and snubbing coefficient). These parameters are influenced by the choice of constituent materials, such as cement type, additives, aggregates, fiber types and volume fraction, and by method of processing. Conventional processing involves mixing and casting, and autoclaving. Nowadays a variety of processing tools are available. These include the control of vacuum and temperature during mixing, vibration frequency during casting, addition of chemical admixtures

technological implication of the PDDA is not just in boosting structural performance, but that PDDA can lead to economy by optimizing the material microstructure and thus using materials most efficiently. On the other hand, the PDDA even when applied narrowly to cementitious composites, reveals many technological and scientific gaps which must be filled for such an approach to be successful. These knowledge gaps involving materials processing, micromechanics, and the translation of material properties to structural performance, represent critical challenges to the research community in the coming decades. They define the research agenda of the ACE-MRL.

SHEAR INTENSIVE STRUCTURES

Engineers have long recognized that concrete must be reinforced when used as a material for large scale structures. For example, a beam under bending load maintains its ductility by yielding of the reinforcing steel. However, it soon becomes obvious that such reinforced concrete members can also fail in shear, and that shear failure can be catastrophic. A case in point is the punching failure of bridge decks⁴. In addition, shear failure has occurred in anchor bolts embedded in concrete⁵, in corbels⁶, and in shear keys of segmental bridges⁷. The connection between beam-columns and the base of shear walls are also likely to be subjected to intensive shear during earthquake loading. The typical diagonal crack patterns in the shear failed structures suggest that the structural shear load induces local tensile failure of the material. This means that the shear capacity of concrete structures is limited by the tensile capacity of the concrete material. For large structures, especially those with acute geometry such as in a shear key, the local tensile failure may occur in the form of fracture. For this reason, extensive research in fracture mechanics of concrete structures has been conducted, e.g. in fracture analysis of anchor bolt failure⁸. For smaller structures, shear failure may be controlled by the tensile strength or strain rather than by fracture properties. This is the well known size effect—transition of failure mode from strength control to fracture control as the concrete structure increases in dimension⁹.

To design against shear failure, additional shear reinforcement has been applied. Even if steel reinforcement is possible and/or rebar congestion is allowed, concrete cracks induced by shear load can be quite large in width, reducing long term structural durability.

The above discussion suggests that for improved structural performance in safety and durability, it would be necessary to design structures subjected

to intensive shear loads with a material which has enhanced properties in tensile strength, strain and fracture energy. Unfortunately ordinary concrete cannot meet any of these criteria. High strength concrete can reach higher tensile and compressive strength, but their strain capacity and fracture energy remains low. The added propensity in brittle fracture failure therefore requires additional steel rebar reinforcement or steel confinement. For ordinary fiber reinforced concrete (FRC) commonly used, the fracture energy can be enhanced by an order of magnitude, but the tensile strength or strain are typically not much improved. We are therefore forced to look at strain-hardened cementitious composites, since strain-hardening typically brings about additional tensile strength and strain capacities beyond those achievable by FRC. Strain-hardened cementitious composites have been created by a variety of processes such as pultrusion or fiber mat lay-up using continuous fibers^{9,10}. Although such materials have shown superior properties, their applications to practical structures are rather limited because of the special processing needs and the expensive labor involved. A different approach using short random fibers has also achieved high tensile strength capacity (although the uniaxial tensile strain capacity and fracture energy has not been clearly measured) in a slurry infiltrated fiber concrete (SIFCON). SIFCON as its name suggests employs a process in which a steel fiber network is infiltrated by cement or mortar slurry. To create the steel fiber network and to achieve good properties, it is typical to use a high fiber volume fraction, from 4 to 25%¹¹.

For new materials development for civil engineering and building applications, it would be useful to keep in mind the following requirements: 1) Tensile properties much above FRC; 2) Easy processing using as much as possible conventional equipment and low labor cost; 3) Low fiber volume fraction; and 4) No material anisotropically weak planes. These requirements seem to be contradictory. However, micromechanical analyses reveal that composites meeting such requirements can be manufactured. In the following sections, we discuss the micromechanics-based rationale for material constituent selections, the tensile properties of such an engineered cementitious composite (ECC), and its application to a simulated shear structure. Comparisons with conventional concrete and shear reinforced (using wire mesh) concrete confirm the advantages expected of ECCs.

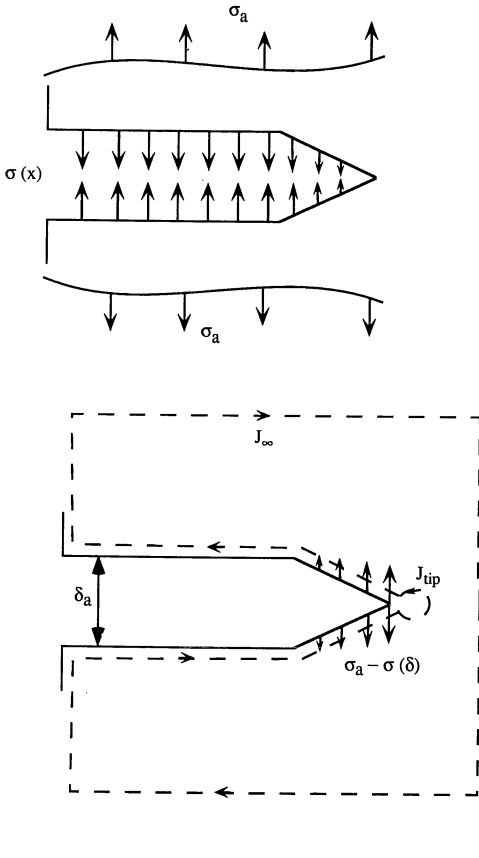


Fig.3 Steady State Cracking (a) Showing Remote Stress, Crack Shape and Traction on Crack; and (b) J-integral Contour on Equivalent Problem (after Marshall and Cox, 1988).

MICROMECHANICS AND MATERIAL CONSTITUENT SELECTION

Steady State Cracking Analysis

Conditions for pseudo strain-hardening has been reviewed by Li and Wu¹²⁾. In that work, the stress approach was utilized resulting in a more conservative requirement due to the assumption of an elliptical crack shape. In the following, we adopt an energy approach suggested by Marshall and Cox¹³⁾ and which does not need to impose any crack shape assumptions. A fundamental requirement of pseudo strain-hardening is that steady state cracking occurs. **Fig.3(a)** shows such a crack propagating under uniform and constant remote tension σ_a . The crack opening is uniform with fiber bridging stress balancing the remote load except for a segment near the crack tip. In this segment the crack opens as the bridging stress rises from zero at the tip to σ_a when this segment joins with the flattened crack segment. The crack opening δ at each point along the crack is directly related to the

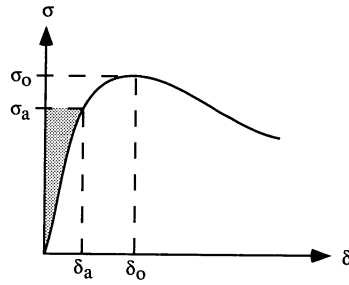


Fig.4 A typical σ - δ Curve of a Discontinuous Fiber Reinforced Cementitious Composites. The shaded area represents the complementary energy. See Eqn. (1) and related text.

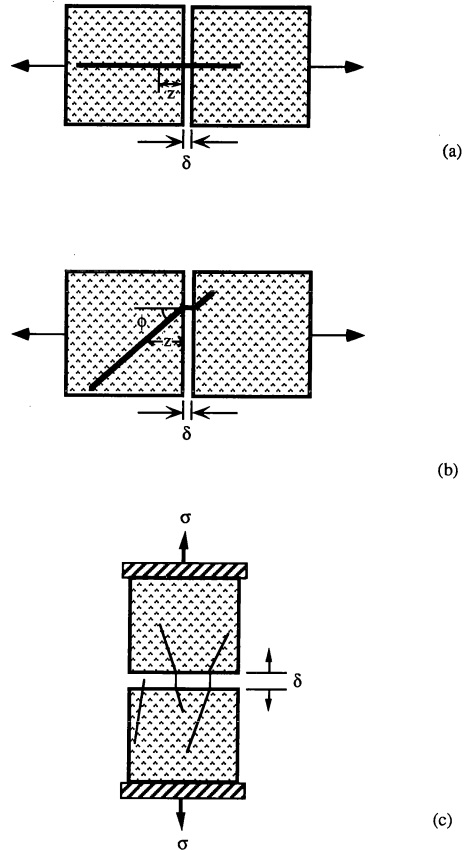


Fig.5 Three Essential Steps in Deriving the σ - δ Relation for Short Random Fiber Reinforced Cementitious Composites (a) Single Fiber Normal Pull-Out. The fiber bridging stress is $\sigma_s(\delta, z)$; (b) Inclined Fiber Pull-Out. The fiber bridging stress is $\sigma_s(\delta, z, \phi)$; (c) Statistical Description of Fiber Distribution.

bridging stress σ as dictated by the details of fiber reinforcement. By making use of the path independent property of the J-integral¹⁴⁾, and after subtracting a uniform stress of σ_a , Marshall and Cox shows that during steady state cracking,

$$J_{tip} = \sigma_a \delta_a - \int_0^{\delta_a} \sigma(\delta) d\delta \dots\dots\dots (1)$$

for the contour shown in Fig.3(b). The right hand side of (1) is interpretable as the complementary energy of the $\sigma-\delta$ curve as indicated by the shaded area in Fig.4. For pseudo strain-hardening, it is required that¹⁵⁾

$$\sigma_a \leq \sigma_0 \dots\dots\dots (2)$$

where σ_0 is the maximum bridging stress corresponding to the maximum opening δ_0 in Figure 4. Hence pseudo strain hardening requires

$$J_{tip} \leq \sigma_0 \delta_0 - \int_0^{\delta_0} \sigma(\delta) d\delta \dots\dots\dots (3)$$

Micromechanics of Normal Fiber Bridging

The micromechanics of fiber bridging has been described by Li¹⁶⁾ for discontinuous fibers of arbitrary randomness. Fig.5 illustrates the three essential steps in deriving the $\sigma(\delta)$ relationship. First the mechanics of a single fiber bridging normally to the crack plane (Fig.5(a)) must be analyzed. Various assumptions concerning the interface properties and mode of failure can be adopted¹⁷⁾. Also, depending on the type of fiber, the bridging stress may be terminated by tensile rupture of the fiber¹⁸⁾. Although there has been a number of theoretical investigations¹⁹⁾⁻²¹⁾ into fracture mode failure of the interface in the form of a tunneling crack, there has been so far no confirmation that such is the case in a fiber reinforced cementitious composite. Shear-lag analysis¹⁹⁾ is typically utilized to relate the single fiber bridging stress σ_s to the crack opening δ :

$$\begin{aligned} \sigma_s(\delta, z) \\ = fnc(\delta, z; \text{fiber properties; interface prop-} \\ \text{erties}) \\ \dots\dots\dots (4) \end{aligned}$$

where the fiber properties may include the fiber modulus, tensile strength, fiber length, and diameter, and the interface properties may include the cohesive strength or fracture properties and frictional properties. The variable z represents the initial distance (at $\delta=0$) between the centroid of the bridging fiber and the matrix crack plane. Hence the embedment length can be calculated from z and δ as the crack opens. Accounting for Poisson's effect of the stretched fiber and residual strain effect has been attempted^{22),23)}. If the fiber is crimped, deformed or with hooked ends, detail accounting of the fiber shape effect on σ_s or an effective interface property should be included in (4).

Micromechanics of Inclined Fiber Bridging

In a composite, fibers often bridge at an angle to the matrix crack. The bridging stress of an inclined fiber (Fig.5(b)) has been analyzed for various assumptions of fiber and matrix behavior. For very flexible fibers with high strain capacity typical of polymeric fibers, a snubbing effect may occur due to the local fiber pressure exerted onto the matrix at the fiber exit point²⁴⁾. The snubbing effect may reduce the critical fiber length leading to premature fiber failure²⁵⁾. For fibers with elastic-plastic behavior typical of steel fibers, local plastic yielding of the fiber at the exit point may occur²⁶⁾. For fibers with elastic brittle behavior such as some carbon or glass fibers, fiber failure may occur due to excessive bending²⁷⁾. In addition, local spalling of the brittle matrix under the fiber has been observed²⁴⁾. This spalling has the effect of relaxing the fiber bridging load. All of these fiber/matrix interactions due to inclined fiber pull-out will alter the bridging stress so that (4) becomes

$$\begin{aligned} \sigma_s(\delta, \phi, z) \\ = fnc \left(\begin{array}{l} \delta, \phi, z; \text{fiber properties; interface properties;} \\ \text{local fiber/matrix interaction properties} \end{array} \right) \\ \dots\dots\dots (5) \end{aligned}$$

where ϕ is the inclination angle of the fiber to the matrix crack plane. It should be noted that aging effects can be introduced into (5) by recognizing that the interfacial properties and the fiber/matrix interaction properties change with age. For example Li and Chan²⁸⁾ observed that interfacial friction bond strength improve with age in a manner similar to that of cement hydration for a steel fiber in a cement matrix. Age effects were also studied by Katz and Bentur²⁹⁾ in relation to modulus of rupture measurements for carbon fiber reinforced cement composites. They observed that the modulus of rupture first increases and then decreases with age, suggesting that higher amount of fiber breakage occurs either due to increase bond or due to bending of fibers on a stiffer foundation.

Fiber Volume Fraction and Distribution

Finally, the finite length and the random orientation of the fibers dictate the amount of bridging fibers carrying load across the matrix crack (Fig.5(c)). These effects are described by probability density functions $p(z)$ and $p(\phi)$. The volume fraction of fibers with centroid located between z and $z+dz$, and with inclination angle between ϕ and $\phi+d\phi$ will be given by $V_f p(\phi) p(z) dz d\phi$, where V_f is the total fiber volume fraction in the composite.

Composite σ - δ Relation

The combined mechanistic effect of fiber bridging and the statistical effect of fiber distribution must be brought together to represent the composite $\sigma(\delta)$ relationship¹⁶⁾:

$$\sigma(\delta) = V_f \int_{\phi=0}^{\pi/2} \int_{z=0}^{(L_f/2)\cos\phi} \sigma_s(\delta, \phi, z) p(\phi) p(z) dz d\phi \quad \dots\dots\dots (6)$$

The upper integration limit on z ensures the counting of only those fibers which actually bridge the crack. Fibers far from the crack plane or close but lying at an oblique angle so that they do not actually cross the crack are therefore not included in the bridging action of the composite. The integration limits should be modified when fibers fail and stop contributing to the composite bridging stress²⁵⁾. Once σ_s , $p(\phi)$, and $p(z)$ are determined, eqn. (6) can be used to determine the composite $\sigma(\delta)$. For steel and brass fibers in a cementitious composite, Li and Chan²⁷⁾ determined that the failure is controlled by a simple frictional strength τ . Further it appears that a snubbing effect representing a flexible rope passing over a friction pulley works reasonably well^{16,24)} for steel and polymeric fibers. These considerations lead to a simple form of σ_s :

$$\sigma_s(\delta, \phi, z) = \begin{cases} [4\tau(1+\eta)E_f\delta/d_f]^{1/2}e^{f\phi} & \text{for } 0 \leq \delta \leq \delta_p \\ [4\tau(\ell + \delta_p - \delta)/d_f]e^{f\phi} & \text{for } \delta_p \leq \delta \leq \ell \\ 0 & \text{for } \ell \leq \delta \end{cases} \quad \dots\dots\dots (7)$$

where $\eta = (V_f E_f)/(V_m E_m)$, and $\ell = L_f/2 - z/\cos\phi$ is the embedment length of a fiber located at z and with an inclination angle ϕ (**Fig.5(b)**). Also $\delta_p = 4\tau\ell^2/[E_f d_f(1+\eta)]$ is the crack opening at which a fiber with embedment length ℓ will start to slip out on completion of frictional debonding. The coefficient f is a fiber/matrix interaction factor known as the snubbing friction coefficient²⁴⁾ which must be experimentally determined for a given pair of fiber and matrix.

By further assuming a uniform 3-D random distribution of fibers so that $p(z) = 2/L_f$ and $p(\phi) = \sin\phi$, the $\sigma(\delta)$ relationship has been derived¹⁶⁾:

$$\sigma(\delta) = \begin{cases} \sigma_0[2(\delta/\delta_0)^{1/2} - (\delta/\delta_0)] & \text{for } \delta \leq \delta_0 \\ \sigma_0(1 - 2\delta/L_f)^2 & \text{for } \delta_0 \leq \delta \leq L_f/2 \\ 0 & \text{for } L_f/2 \leq \delta \end{cases} \quad \dots\dots\dots (8)$$

where $\sigma_0 = g\tau V_f L_f/(2d_f)$ is the maximum bridging stress corresponding to a crack opening of $\delta_0 = \tau L_f^2/[E_f d_f(1+\eta)]$, and $g = 2(1 + e^{f\pi/2})/(4 + f^2)$.

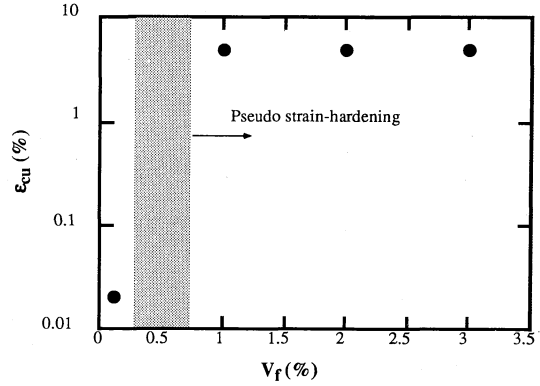


Fig.6 Strain Capacity of Spectra ECC for Various Fiber Volume Fractions. The estimated critical fiber volume fraction is indicated by the shaded strip.

Table 1 Properties of Fiber, Matrix and Interface Used in the Spectra ECC

Fiber			Matrix			Interface	
d_f (μm)	L_f (mm)	E_f (GPa)	K_m (MPa $\sqrt{\text{m}}$)	E_m (GPa)	v_m	τ (MPa)	g
38	12.7	120	0.2-0.3	15	0.25	0.7-1	1-1.5

Requirements for pseudo strain-hardening

Using eqn. (8) in (3) then results in

$$V_f \geq V_f^{crit} \equiv \frac{12J_{tip}}{g\tau(L_f/d_f)\delta_0} \quad \dots\dots\dots (9)$$

Note that eqn. (9) expresses the condition for pseudo strain-hardening in the form of a critical fiber volume fraction V_f^{crit} which must be exceeded to create a composite with high strain capacity. V_f^{crit} is defined in terms of measurable micromechanical parameters involving matrix properties, fiber properties, interface property and fiber/matrix interaction property. To create pseudo strain-hardening with minimum amount of fiber, it is preferable to aim at low V_f^{crit} . Therefore low matrix toughness (J_{tip}), strong interfacial bond and snubbing friction, high aspect ratio of the fiber, and a large δ_0 are favorable to pseudo strain-hardening. It should be noted that (9) has been derived assuming that the fiber does not rupture. Otherwise, it can be shown that V_f^{crit} grows rapidly with decreasing fiber strength.

ENGINEERED CEMENTITIOUS COMPOSITES

As a demonstration of the implications behind the micromechanical concept contained in (9), **Fig.6** shows the significant composite strain capacity change as a result of pseudo strain-hardening for an Engineered Cementitious Composite (ECC) designed with a polypropylene fiber (Spectra 900, manufactured by Allied Corpora-

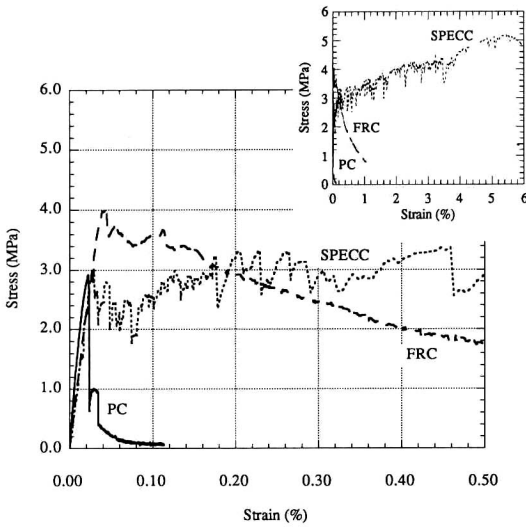


Fig.7 Uniaxial Tensile Stress-Strain Curve of a Spectra ECC ($V_f=2\%$), a Plain Concrete (PC); and a Typical steel FRC.

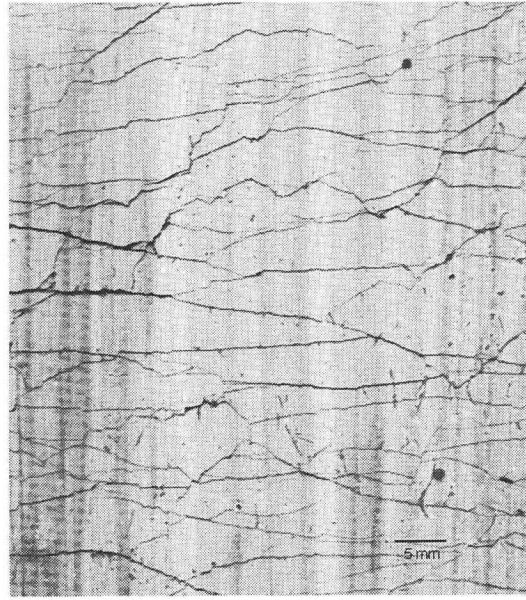


Fig.8 Multiple Cracking in a Spectra ECC ($V_f=2\%$) Uniaxial Tensile Specimen.

tion). Fiber, matrix and interfacial properties are listed in **Table 1**, and the critical fiber volume fraction is determined to be in the range of 0.3–0.7%. Below the critical fiber volume fraction, the composite strain is essentially the same as the cement matrix. Above V_f^{crit} , however, the strain capacity jumps by 2 orders of magnitude to 6%. This Spectra ECC illustrates that by judicious choice of materials composition, it is not necessary to employ extraordinary high fiber volume fraction rendering the material economically infeasible for practical application. Indeed, in terms of composite strain capacity, **Fig.6** reveals that fiber volume fraction much above V_f^{crit} does not bring about further increase in strain capacity. Hence for economic reasons and for ease of processing, it is not recommended that volume fraction much higher than the critical value be used.

The reason for the high strain capacity of ECCs becomes clear when one examines the stress-strain curve (**Fig.7**) and the surface damage of the specimen (**Fig.8**). After first crack, the bridging fibers continue to carry increasing amount of load across this crack, leading to additional cracks elsewhere. This multiple cracking process continues until the maximum bridging stress σ_0 for the $\sigma-\delta$ curve is reached on one of the crack planes. It should be noted that this damage process occurs at increasing load—resulting in a pseudo strain-hardening behavior for the composite. For comparison, the tensile response of a plain concrete (PC) and a typical FRC reinforced with 1% hooked end steel fiber are also shown in **Fig.7**. These latter materials exhibit softening immediately after their

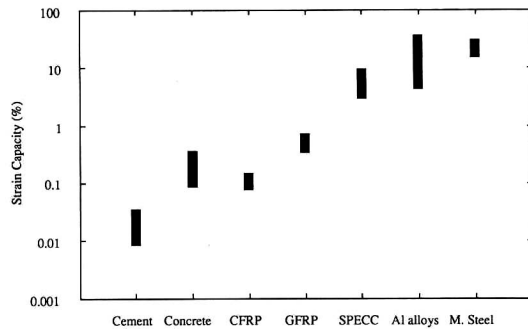


Fig.9 Comparison of Strain Capacity of Spectra ECC with other Structural Materials (adapted from Ashby and Jones, 1984)

first crack strength is reached.

Fig.9 shows the strain capacity at ultimate load of Spectra ECCs, in comparison with other materials. The higher range of strain capacity has been achieved with Spectra fibers which have been pre-treated with a plasma process. It can be seen that the Spectra ECC has achieved a strain capacity comparable to those of aluminum alloys.

The ability to transfer load away from an initial crack in an ECC prompted an investigation of the damage tolerance of such materials. Li and Hashida³⁰ analyzed the damage process at the tip of a notch casted into a Spectra ECC. They found these ECC material failed in a completely different mode compared to common cementitious materials. In neat cement (**Fig.10(a)**), fracture failure occurs in a very brittle manner, consuming a

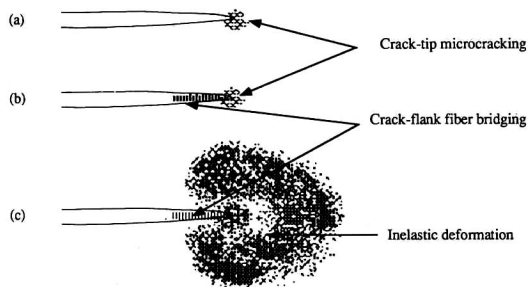


Fig.10 Fracture Failure Mode and Crack Tip Process of Various Cementitious Materials, (a) Neat Cement; (b) Concrete and FRC; and (c) Spectra ECC.

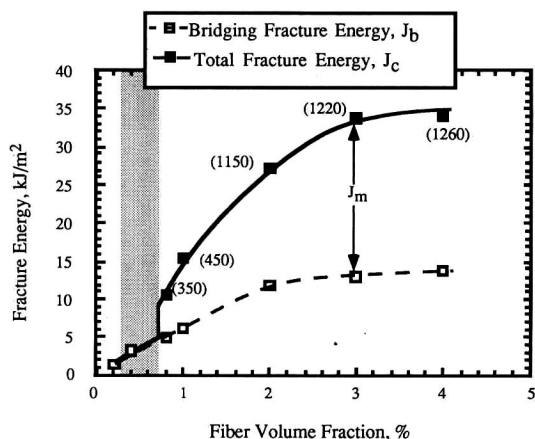


Fig.11 Fracture Energy Measured On- and Off-Crack-Plane of Spectra ECC. The estimated critical fiber volume fraction is indicated by the shaded strip. Numbers in parenthesis indicate the areal dimension of the inelastic process zone in cm^2 .

fracture energy typically on the order of 0.01 kJ/m^2 . In a concrete or fiber reinforced concrete, the fracture process is quasi-brittle due to the presence of a process zone in which aggregate, ligament, or fiber bridging occurs (**Fig.10(b)**). This energy dissipation process typically brings about an order of magnitude increase in fracture toughness, to roughly one to several kJ/m^2 . In the Spectra ECC, in addition to fiber bridging along the crack plane, the load transfer effect causes additional microcracking off the crack plane (**Fig.10(c)**), thus creating an extensive inelastic energy absorption process and causing the macro-behavior to assume an almost ductile fracture mode.

Fig.11 shows the experimentally measured on- and off-crack-plane fracture energy³¹⁾. The on-crack-plane fracture energy J_b has been determined from the area under the descending branch of a uniaxial tensile test. The off-crack-plane fracture energy J_m has been determined from the total

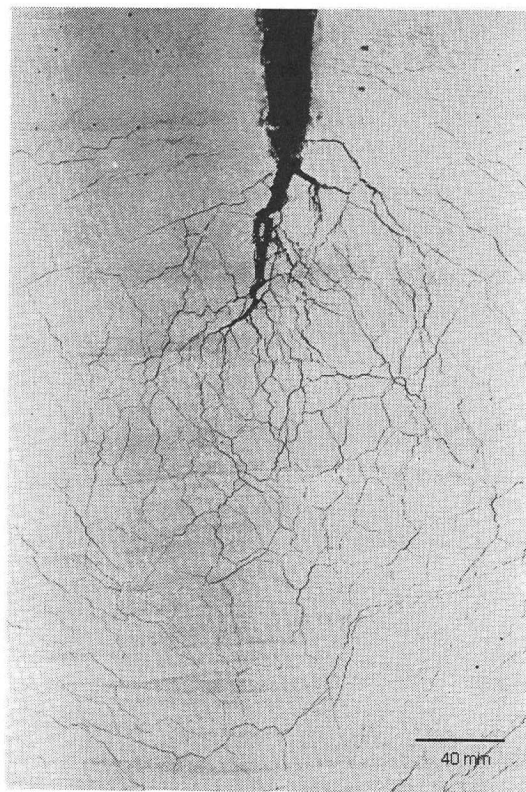


Fig.12 Extensive Damage Development near the Crack Tip in a Spectra ECC ($V_f=2\%$) Fracture Specimen.

fracture energy J_c based on the J-integral technique, less the on-crack-plane fracture energy. It is seen that the off-crack-plane fracture energy is non-existent when the fiber volume fraction is below the critical value V_f^{crit} . Above V_f^{crit} , however, the off-crack-plane fracture energy increases and eventually exceeds that of the fiber bridging energy consumed on the crack plane. From this investigation, it is clear that the ductile fracture mode is closely associated with the condition of pseudo strain-hardening. The off-crack-plane fracture energy is considered to have derived from the frictional debonding process of the fibers crossing the off-crack-plane microcracks. **Fig.12** shows the extensive damage crack tip zone in a 2% Spectra ECC which failed in a ductile fracture mode. The total fracture energy of the Spectra ECC has reached $10\text{--}35 \text{ kJ/m}^2$. This is at least three orders of magnitude higher than that of the cement matrix. Apart from the much higher fracture energy level, it is expected that the R-curve behavior of ECCs will be much steeper so that the steady state fracture energy can be accessed with much shorter cracks in comparison with ordinary FRC in which the full fracture energy

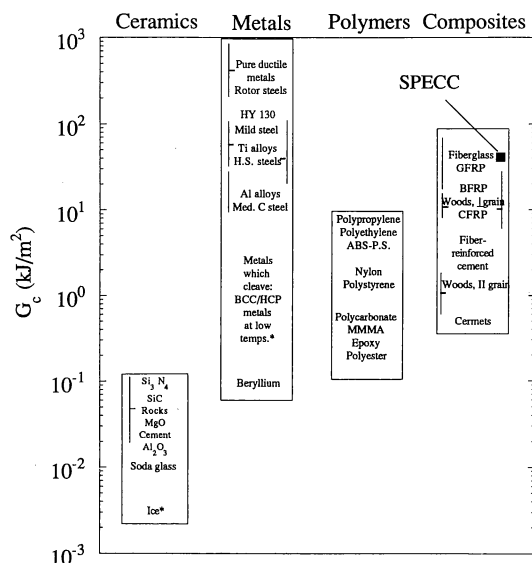


Fig.13 Comparison of Fracture Energy of Spectra ECC with other Structural Materials (adapted from Asbhy and Jones, 1984).

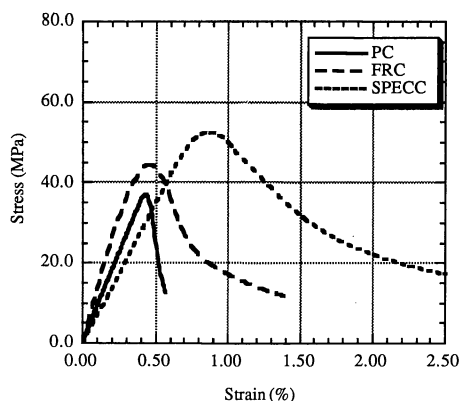


Fig.14 The Compressive Stress-Strain Relation for the Spectra ECC. Also shown are Test Curves for Plain Concrete (PC) and for a typical FRC.

can only be tapped when the fracture process zone has reached an opening equal to half the fiber length. For many applications, this implies such large cracks that the structure would have been rendered unserviceable. The expected R-curve behavior of ECC, however, has not yet been confirmed.

Fig.13 shows a comparison of the fracture energy of various materials including that of Spectra ECC. It is seen that the damage tolerance of this ECC is quite comparable to those of FRP, and competes with some structural metals. For example, the fracture energy of typical aluminum alloys are in the range of 8-30 kJ/m² ³²⁾.

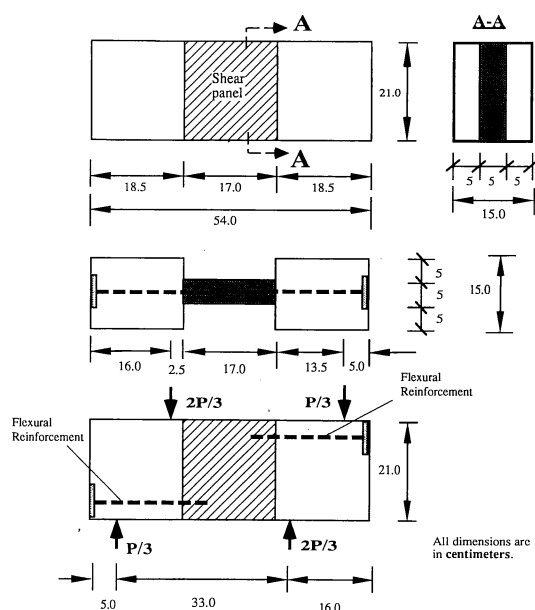


Fig.15 Ohno Shear Beam Geometry, Dimension and Loading Configuration.

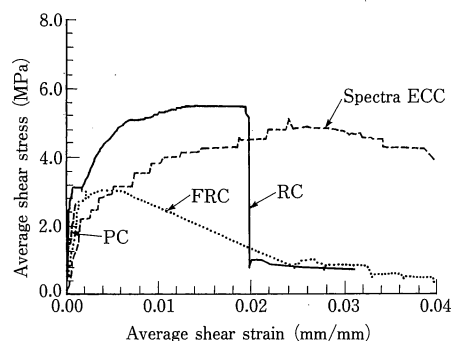


Fig.16 Experimentally Determined Averaged Shear Stress-Strain Relation for Various Cementitious Systems.

SHEAR PERFORMANCE

For the purpose of investigating the performance of shear intensive structures, we have chosen a 2% Spectra ECC which has the tensile behavior shown in Fig.7. The compressive strength and strain of this ECC is also quite reasonable in comparison to typical cementitious materials. Fig.14 shows the compressive stress-strain curves for the ECC, as well as those for the PC and FRC with tensile response shown in Fig.7.

The shear test³³⁾ was aimed at clarifying the shear load carrying capability of the cementitious material so that contribution of axial reinforcement was minimized as much as is possible. The Ohno Shear Beam³⁴⁾ was chosen with geometry, dimension and

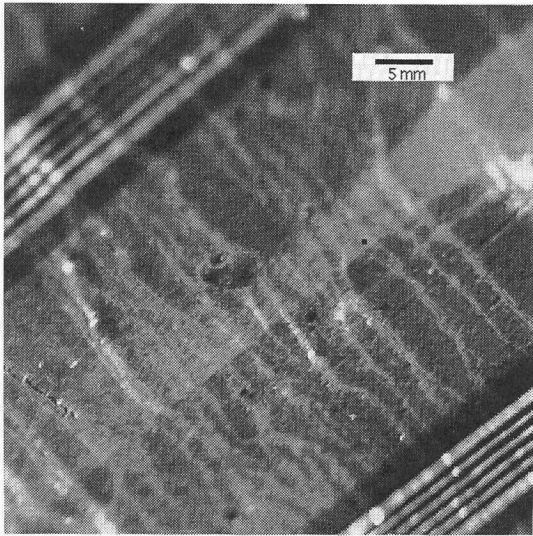


Fig.17 Hair-line Diagonal Multiple Cracking in the Spectra ECC Ohno Shear Beam. Two Strain Gages are also shown.

loading configuration shown in **Fig.15**. Apart from the PC and FRC mentioned earlier, a steel wire mesh reinforced concrete (RC) was also included in the shear test as a simulation of a structure with conventional shear reinforcements (1.5% volume fraction).

The measured averaged shear stress versus strain for the various material systems are shown in **Fig.16**. It is seen that the first crack strength in all systems are approximately the same. The post-first crack strength behavior, however, are decidedly different. The PC beam fails brittly, with no residual strength after the formation of a large diagonal crack. The FRC beam shows a softening branch associated with pull-out of the steel fibers across a single major crack with increasing crack width. The RC beam reveals good load bearing capacity after first crack. As the major (typically one or two) cracks open, concrete spalls form and expose the wire mesh which appear to show localized deformation associated with the peak load. For the ECC beam, localized cracking did not occur beyond first crack. Instead, the composite spreads the damage. As the beam continues to be loaded, hair line sub-parallel diagonal cracks appear on the mid-section of the beam (**Fig.17**). This beam reaches the highest ductility before load softening occurs, despite the fact that it has no steel reinforcement at all. Thus it is clear that the strain-hardening advantages designed into the Spectra ECC material was translated into the improved shear response of the structural beam.

Apart from the safety performance when loaded

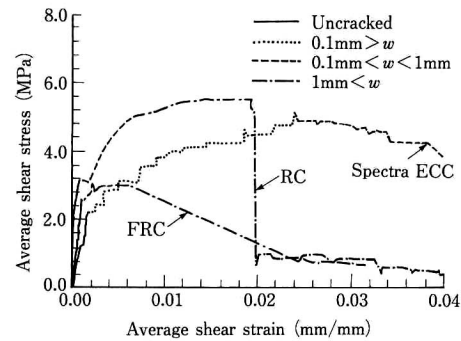


Fig.18 Crack Width Development for the Various Cementitious Systems in the Ohno Shear Beam

beyond first crack strength, the Spectra ECC beam also suggest potential durability performance improvement. The spreading of the damage rather than the continued opening of one or two cracks to large crack widths suggest that prevention of aggressive agent penetration into the interior of the structure will be minimized by the ECC. Penetration of aggressive agents have been identified as the major cause of reinforcement, prestressing or post-tensioning tendon corrosion in concrete structures. **Fig.18** shows the crack width development for the various cementitious systems at different loading stages. In addition, the rising load as the structure deforms inelastically indicates that energy absorption of structures built with ECC materials can be a significant performance improvement especially when used in seismic resistant structures. This aspect is now being investigated at the ACE-MRL in connection with the use of ECC as a plastic hinge near a beam-column connection.

CONCLUSIONS AND FUTURE DEVELOPMENTS

This paper surveys the adoption of the performance Driven Design Approach in the development of a strain-hardening Engineered Cementitious Composite designed for shear intensive structures. A major link between structural performance and material structure tailoring is provided by micromechanics tools. By proper selection of fiber, matrix and interface, it is demonstrated that a composite with improved strength, strain and fracture energy properties can be manufactured, and that the amount of fiber reinforcement does not necessarily have to be excessively high. This last aspect make it possible to achieve cost-effectiveness, and the structural performance in safety, durability and energy absorption capacity further justifies the practical application of this new class of materials.

The Spectra ECC described in this paper is but

one of several ECC materials being developed at the ACE-MRL. ECCs with steel, carbon and other polymeric fiber types are being investigated. In addition, ECCs with aggregates are also being developed.

Apart from shear properties, energy absorption properties under low cycle reversed loading are being investigated, as alluded to before for earthquake resistant structures. In addition, the limited Ohno Shear beam tests described in this paper also indicates beneficial effects of lateral compression in enhancing the biaxial property of ECC over that of the uniaxial tensile properties³³⁾. Fatigue properties are also being researched, and micromechanical models will be used to relate structural high cycle fatigue performance to micromechanical properties. And of course the fundamental tensile properties, some of which elaborated in this paper, will continue to receive attention with respect to influence of fiber, matrix and interface properties. These properties are strongly influenced by processing conditions so that details of their effects must be carefully analyzed.

As is clear from the discussions in the main text, a high performance cementitious composite must be defined in terms of the structural application it is intended for. It is envisioned in future that specific ECCs can be designed for structural members employed for different functions. This approach should lead to optimal use of expensive components in the ECCs. In other words, additional cost of the material must be more than off-set by the performance boost in the overall structural system. The PDDA provides a conceptual framework for the first step towards this ideal. Successful technological implementation, however, cannot be achieved without the participation of industrial partners.

ACKNOWLEDGMENTS

The ACE-MRL at the University of Michigan is sponsored by a consortium of government and industrial institutions. These include the National Science Foundation, the Air Force Office of Scientific Research, the National Research Council, the Conoco Corporation, the Shimizu Corporation, and the US Gypsum Corporation. Their generosity and the support of the college of Engineering at the University of Michigan, are gratefully acknowledged. Collaborations with various universities have been most rewarding. Of special mention are H.Krenchel and S.Stang at the Technical University of Denmark and T.Hashida at Tohoku University in Sendai, Japan. Many members at the ACE-MRL contributed to work described directly or indirectly in this paper. They

include Y.W.Chan, O.Karthekeyan, A.Katz, J.Lafave, Y.M.Lim, M.Maalej, T.Matsumoto, D.K.Mishra, A.Naaman, J.Wight, and H.C.Wu.

REFERENCES

- 1) Hasegawa, F. : *Built by Japan—Competitive Strategies of the Japanese Construction Industry*, Wiley Interscience, 1988.
- 2) Li, V.C. : Performance Driven Design of Fiber Reinforced Cementitious Composites, in *Proceedings of 4th RILEM International Symposium on Fiber Reinforced Concrete*, Ed.R.N.Swamy, pp.12-30, Chapman and Hall, 1992.
- 3) National Research Council : *Materials Science and Engineering for the 1990s*, Pub. National Research Council, 1990.
- 4) Csagoly, P.F : Design of Thin Concrete Deck Slabs by the Ontario Highway Bridge Design Code, Ontario Ministry of Transportation and Communications, 1979.
- 5) Eligehausen, R. and Sawade, G. : A Fracture Mechanics Based Description of the Pull-Out Behavior of Headed Studs Embedded in Concrete, in *Fracture Mechanics of Concrete Structures*, pp.281-299, 1989.
- 6) Nguyen, N.T. : Reinforced Concrete Corbel-A Case Study, MSc Thesis, The Massachusetts Institute of Technology, 1988.
- 7) Lamberson, E.A., and J.M. Barker : Kishwaukee River Bridges, *Concrete International*, August, pp.93-101, 1981.
- 8) Bazant, Z. : Should Design Codes Consider Fracture Mechanics Size Effect? In *Concrete Design Based on Fracture Mechanics*, *ACI SP-134*, pp.1-24, 1992.
- 9) Krencher, H., and H. Stang : Stable Microcracking in Cementitious Materials, in *Proceedings of 2nd Int'l Symp. on Brittle Matrix Composites*, Ed.A.M.Brandt, I.H.Marshall, pp.20-33, 1988.
- 10) Swamy, R.N : Structural Implications of High Performance Fibre Cement Composite, in *High performance Fiber Reinforced Cement Composites*, Ed. H.W. Reinhardt and A.E. Naaman, pp.529-543, 1992.
- 11) Naaman, A. : SIFCON; Tailored Properties for Structural Performance, in *High Performance Fiber Reinforced Cement Composites*, Ed. H.W. Reinhardt and A.E. Naaman, pp.18-38, 1992.
- 12) Li, V.C., and H.C. Wu : Conditions for Pseudo Strain-Hardening in Fiber Reinforced Brittle Matrix Composites, *J.Applied Mechanics Review*, V.45, No.8, August, pp.390-398, 1992.
- 13) Marshall, D. and B.N. Cox : A J-Integral Method for Calculating Steady-State Matrix Cracking Stress in Composites, *Mechanics of Materials*, 7, pp.127-133, 1988.
- 14) Rice, J.R. : A path independent integral and the approximate analysis of Strain Concentrations by Notches and Cracks, *J.Appl.Mech.*35, pp.379-386, 1968.
- 15) Li, V.C. and Leung, C.K.Y. : Steady State and Multiple Cracking of Short Random Fiber Composites, *ASCE J. of Engineering Mechanics*, Vol.118, No.11, pp.2246-2264, 1992.
- 16) Li, V.C. : Post-Crack Scaling Relations for Fiber Rein-

- forced Cementitious Composites, *ASCE J. of Materials in Civil Engineering*, V.4, No.1, pp.41-57, 1992.
- 17) Leung, C.K.Y., and V.C. Li : Strength Based and Fracture Based Approaches in the analysis of fiber debonding, *J. Materials Science Letters*, 9, pp.1140-1142, 1990.
 - 18) Li, V.C., M. Maalej, and T. Hashida : Optimization of Discontinuous Fiber Composites, in *Proc. ASCE 9th Engin.Mech.Conf.*, Eds. L.D. Lutes & J.M. Niedzwecki, published by ASCE, pp.1000-1003, 1992.
 - 19) Stang, H., and S. Shah : Characterization of Interfacial Bond in FRC Materials, in *Toughening Mechanisms in Quasi-Brittle Materials*, Ed. by S.P. Shah, pp.507-528, 1991.
 - 20) Gao, Y., Mai, Y.W. and Cotterell, B. : Fracture of Fiber Reinforced Materials, *J. Appl. Math. Phys. (ZAMP)* 39, pp.550-572, 1988.
 - 21) Leung, C.K.Y. : Fracture Based Two-Way Debonding Model for Discontinuous Fibers in Elastic Matrix, *ASCE J. Engineering Mechanics*, Vol.118, No.11, pp.2298-2319, 1992.
 - 22) Takaku, A. and R.G.C. Arridge : The Effect of Interfacial Radial and Shear Stress on Fiber Pull-Out in Composite Materials, *J. Phys. D : Appl. Phys.*, Vol.6, pp.2038-2047, 1973.
 - 23) Sigl, L.S. and A.G. Evans : Effects of Residual Stress and Frictional Sliding on Cracking And Pull-Out in Brittle Matrix Composites, *Mechanics of Materials*, 8, pp.1-12, 1989.
 - 24) Li, V.C., Y. Wang, and S. Backer : Effect of Inclining Angle, Bundling, and Surface Treatment on Synthetic Fiber Pull-Out from a Cement Matrix, *J. Composites*, Vol.21, 2, pp.132-140, 1990.
 - 25) Maalej, M., V.C.Li, and T. Hashida : Effect of Fiber Rupture on Tensile Properties of Short Fiber Composites, Submitted for publication in the *ASCE J. of Engineering Mechanics*, 1993.
 - 26) Morton, J. and Groves, G.W. : The cracking of Composites Consisting of Discontinuous Ductile Fibers in a Brittle Matrix—Effect of Fiber Orientation, *J. Mat. Sci.*, 9, pp.1436-1445, 1974.
 - 27) Leung, C.K.Y., and V.C. Li : Effect of Fiber Inclination on Crack Bridging Stresses in Fiber Reinforced Brittle Matrix Composites, *J. Mechanics and Physics of Solids*, Vol.40, pp.1333-1362, 1992.
 - 28) Li, V.C. and Y.W. Chan : Determination of Interfacial Debonding Mode for Fiber Reinforced Cementitious Composites, submitted to *J. Amer. Cera. Soc.*, 1993.
 - 29) Katz, A., and A. Bentur : High Performance Fibres in High Strength Cementitious Matrices, in *High Performance Fiber Reinforced Cement Composites*, Ed. H.W. Reinhardt and A.E. Naaman, pp.237-247, 1992.
 - 30) Li, V.C. and T. Hashida : Engineering Ductile Fracture in Brittle Matrix Composites Accepted for publication in *J. of Materials Science Letters*, 1992.
 - 31) Li, V.C., M. Maalej and T. Hashida : Effect of Fiber Volume Fraction on the Off-Plane Fracture Energy In Ductile Fiber Cementitious Composites, in preparation, 1993.
 - 32) Ashby, M.F. and D.R.H. Jones : Engineering Materials, An Introduction to their Properties and Applications, Pergamon, 1984.
 - 33) Li, V.C., A.E. Naaman, J.K. Wight, D.K. Mishra, J.M. LaFave, H.C. Wu and Y. Inada : On the Shear Behavior of Engineered Cementitious Composites, Submitted for publication in the *J. of Advanced Cement Based Materials*, 1993.
 - 34) Arakawa, T. and K. Ohno : Shear Tests of Reinforced Concrete Beams by Special Type of Loading, Transactions of the Architectural Institute of Japan, Vol.57, pp.581-584. (In Japanese)

(Received March 31, 1993)

著者プロフィール

Li 先生はミシガン大学土木工学科に勤務され、先端土木材料研究所の所長として活躍する新進気鋭の研究者でいらっしゃいます。つい最近教授への昇進が決定したとうかがっています。1954 年のお生まれですからかなり早い昇進であります。今回この研究展望に Li 先生をご推薦したのは、Li 先生が応用力学をベースにした材料開発という新しい分野を開拓しておられるからです。Li 先生は学部・修士・博士ともブラウン大学で修めておられますが、Ph.D. は破壊力学・応用力学の分野で世界的権威である J. R. Rice 教授のご指導で1981年に取得されております。テーマは破壊力学の地震の問題に対する適用に関するもので、Li 先生のバックグラウンドはまさに応用力学であります。セメント系複合材料の開発に関する研究は1981年から1990年まで教鞭をとられたマサチューセッツ工科大学時代より着手され、現在のミシガン大学に移られてからも精力的に続けられ、先端土木材料研究所開設につながったとお聞きしています。セメント系複合材料の開発は、ノースウェスタン大学の Shah 教授を中心に NSF 先端セメント系材料科学技術研究センターが設けられたように、ひとつのホットテーマになっていますが、Li 先生の切り口は、材料の内部で生じている微視的現象を捉え、力学的にモデル化し、定量的に新材料の開発・設計を行おうというものであります。日本においても、力学をベースとする研究者が取り組むべき問題ではないかと考え、推薦させていただいた次第であります。

(東京大学工学部土木工学科 堀井 秀之)